


AM 0/8-680 Coating

Client : Quality Control Argex
0032/32.50.15.15

lab	Quality Control Argex 0032/32.50.15.15
Aggregate Size	0/8 mm
Certifications	EN 13055 : . (1/01/2004)

Essential char. - performance	Minimum	Average	Maximum	Declared	Standard
Loose Bulk Density (+- 15% of declared value)	580	779 kg/m ³	780	680	EN 1097-3
Oven-Dried Particle Density (+- 15% of declared value)	1000	1162 kg/m ³	1300	1150	EN 1097-6 annex C
Freezing & Thawing Resistance		2.3 %	3.3		NF P18-545
Volume Stability		0.22 %	0.50		EN 1367-8
Water Content (from silo)	0.0	11.0 %	14.0		EN 1097-5
Water Absorption 2h	6.00	9.64 %	12.00		EN 1097-6 annex C
Water Absorption 30'	5.00	8.00 %	11.00		EN 1097-6 annex C
Water Absorption 5'	4.00	6.72 %	10.00		EN 1097-6 annex C
Active alkalines content (Na ₂ O eq.)		0.044 %			LPC 37
Alkali - reactivity (qualification)		No Reactive (NR)			FD P18-542
Chloride		0.005 %	0.010		EN 1744-1
Total Sulphur		0.26 %	0.55		EN 1744-1
Acid-Soluble Sulfate		0.071 %	0.500		EN 1744-1

Grading (EN 933-1)				
sieve (mm)	mini	% passing	maxi	Declared
0.000		0.0		
0.063		5.0		
0.125		8.5		
0.250		10		
0.500		13		
1.000		18		
2.000		30		
3.150		41		
4.000		50		
6.300		79		
8.000	90	98	100	
10.000		100		

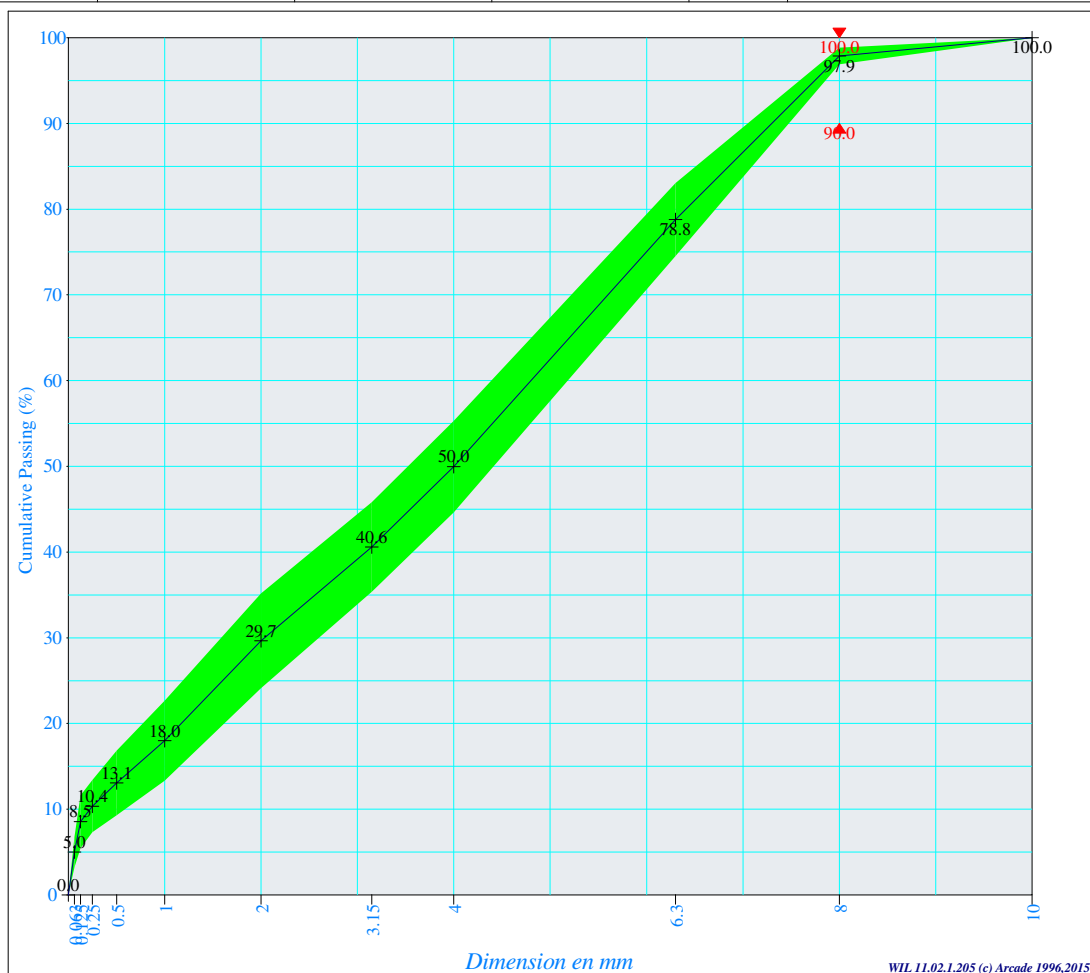

WIL 11.02.1.205 (e) Arcade 1996,2015