


# AR 2/6-500 - Bag

Client : Quality Control Argex  
 0032/32.50.15.15

<b>lab</b>	Quality Control Argex 0032/32.50.15.15
<b>Aggregate Size</b>	2/6.3 mm
<b>Certifications</b>	EN 13055 : . (1/01/2004)

Essential char. - performance	Minimum	Average	Maximum	Declared	Standard
Particle Shape		Round			EN 13055
Crushing Resistance (T-2x30")	1.85	3.00 N/mm <sup>2</sup>	4.00		EN 13055
Estimated Oven-Dried Particle Density (+- 15% of declared)	744	959 kg/m <sup>3</sup>	1006	875	
Loose Bulk Density (+- 15% of declared value)	425	548 kg/m <sup>3</sup>	575	500	EN 1097-3
Freezing & Thawing Resistance		2.3 %	3.3		EN 1367-7
Los Angeles + Micro Deval (4-6.3)		NPD			EN 1097-1 & 2
Los-Angeles (4-6.3)		NPD			EN 1097-2
Polished Stone Value		NPD			EN 1097-8
Volume Stability		0.22 %	0.50		EN 1367-8
Water Content ( from silo )	0.0	1.0 %	5.0		EN 1097-5
Water Absorption 5'		NPD			EN 1097-6
Water Absorption 30'		NPD			EN 1097-6
Water Absorption 24h		NPD			EN 1097-6
Alkali Silica Reactivity		NPD			EN 13055
Chloride		0.005 %	0.010		EN 1744-1
Cleanliness		Pass			EN 1744-1
Release Of Dangerous Substances		NPD			EN 13055
Reaction To Fire		Euroclass A1			EN 13501-1
Total Sulphur		0.44 %	0.55		EN 1744-1
Acid-Soluble Sulfate		0.400 %	0.500		EN 1744-1

Grading ( EN 933-1 )				
sieve (mm)	mini	% passing	maxi	Declared
0.000		0.0		
0.063		1.0		
0.125		1.4		
0.250		1.4		
0.500		1.6		
1.000		2.6		
2.000	0.0	2.8	3.0	
3.150		48		
4.000		64		
5.000		90		
6.300	90	100	100	

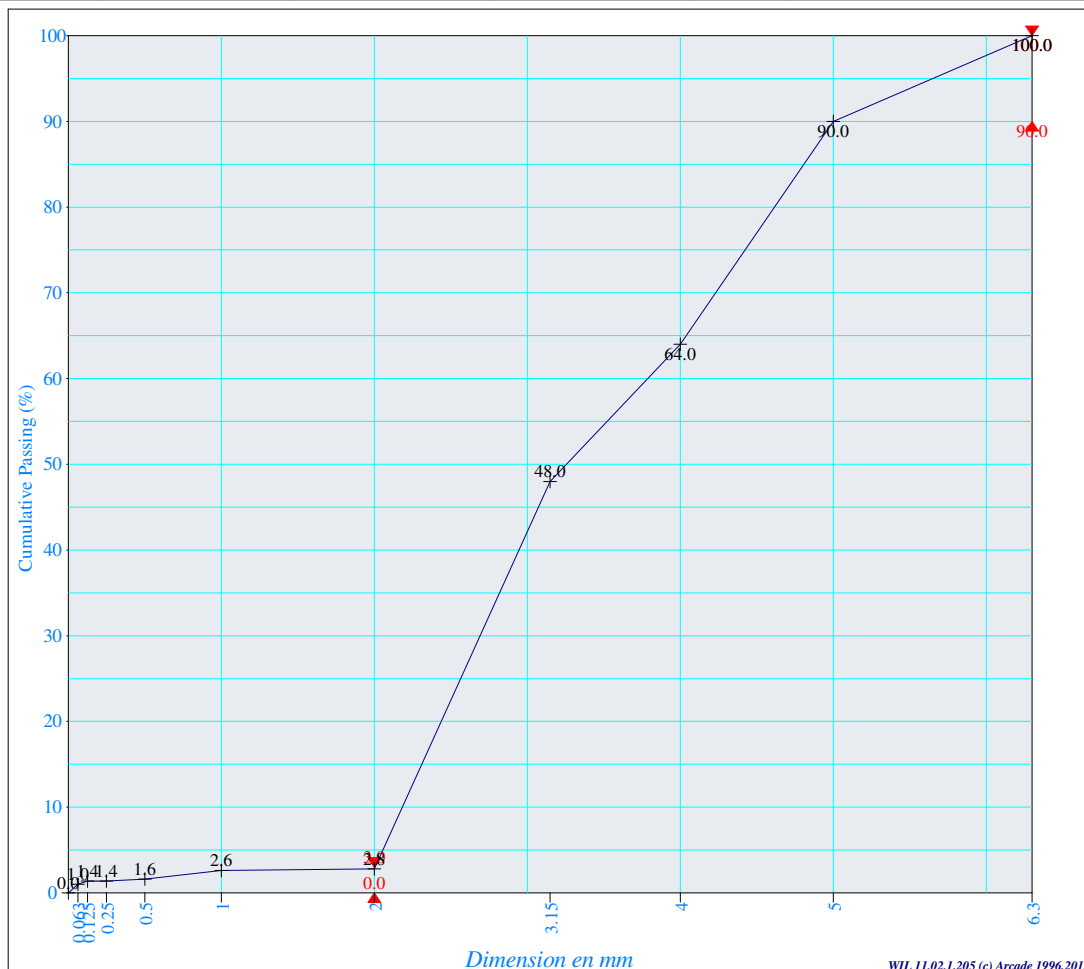

WIL 11.02.1.205 (c) Arcade 1996,2015